

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) PREPARATION OF MIXED PEROVSKITE OXIDES FOR BLUE-GREEN LASERS		5. TYPE OF REPORT & PERIOD COVERED Annual Summary October, 1982-Jan., 1984
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) R.F. Belt and R. Uhrin		8. CONTRACT OR GRANT NUMBER(s) N 00014-83-C-0072
9. PERFORMING ORGANIZATION NAME AND ADDRESS Airtron Division, Litton Industries, 200 E. Hanover Ave. Inc. Morris Plains, N.J. 07950		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 379-050 / 410
11. CONTROLLING OFFICE NAME AND ADDRESS Defense Contract Administration Ser- vices 240 Route 22 Springfield, N.J. 07081		12. REPORT DATE February, 1984
		13. NUMBER OF PAGES vii + 39
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) Office of Naval Research Department of the Navy 800 No. Quincy Street Arlington, Virginia 22217		15. SECURITY CLASS. (of this report) Unclassified
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) None.		
18. SUPPLEMENTARY NOTES None.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Laser Crystals Blue-green Lasers Perovskites Czochralski Growth $\text{La}_2\text{O}_3\text{-Al}_2\text{O}_3\text{-Sc}_2\text{O}_3$ Phase Studies		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Mixed crystals of the perovskite type structure of the system $\text{La Al}_{1-x}\text{Sc}_x\text{O}_3$ were examined over the compositions of $x=0.15\text{-}0.30$ . Single crystals were grown from melts in iridium crucibles using the Czochralski method. Seed crystals of {111} pure $\text{La Al O}_3$ were used. The growth atmosphere was controlled at 99.75% $\text{N}_2$ and 0.25% $\text{H}_2$ . Dopants of $\text{Ce}^{3+}$ were maintained at 0.01-0.05 atomic per cent.		

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Preliminary work on polycrystalline materials showed that blue-green luminescence at 485 nm was found. The grown crystals had various amounts of Sc incorporated and were usually translucent. At the  $x=.30$  formulation of melt, about 60 - 75% of Sc is believed to enter the crystal. No direct evidence was found for ordered type structures. The phase data, compositions, crystal quality, luminescence data, and x-ray results are discussed.

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Unclassified

PREPARATION OF MIXED  
PEROVSKITE OXIDES FOR  
BLUE-GREEN LASERS

by

R.F. Belt and R. Uhrin

Annual Summary Report  
October 1, 1982 - January 31, 1984  
Contract No. N 00014-83-C-0072

Airtron Division  
Litton Industries, Inc.,  
200 East Hanover Avenue  
Morris Plains, New Jersey 07950

February 1984

NOTICES

Approved for public release; distribution unlimited. This research was sponsored by the Office of Naval Research, Department of the Navy, Physics Program, 800 North Quincy Street, Arlington, Virginia 22217. Qualified requesters may obtain copies of this report from Defense Documentation Center, Cameron Station, Alexandria, Virginia 22314. Destroy this report if no longer needed; do not return to sender.

#### NOTICES

The findings in this report are not to be construed as an official Department of the Navy position unless designated by other authorized documents.

The citation of trade names or names of manufacturers in this report should not be taken as official Government endorsement or approval of commercial products or services referenced herein.

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder of any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.



## TABLE OF CONTENTS

	Page
DD Form 1473	i
Table of Contents	ii
List of Figures	iii
Foreword	iv
1.0 Introduction	1
2.0 Experimental Procedures	4
2.1 Materials for Compositions	4
2.2 Crucibles Used	7
2.3 Seed Crystals	8
2.4 Growth Station	9
2.5 Run Technique	12
2.6 Crystal Compositions	13
2.7 Atmospheres for Growth	14
2.8 Doping Levels of Ce <sup>3+</sup>	15
2.9 Evaluation of Crystals	15
3.0 Results of Growth Runs	17
3.1 Run Description	17
3.2 X-ray Data	28
3.3 Visual, Microscopic, Optical	34
3.4 Discussion	36
3.5 Recommendations	37
4.0 Conclusions	37
5.0 References	39
6.0 Distribution List	40

## LIST OF FIGURES

<u>Figure #</u>	<u>Title</u>	<u>Page</u>
1	Czochralski Growth Station	10
2	Drawing of Basic Growth Station	11
3	Crystallized melt obtained by seeding with an iridium wire	19
4	Initial $\text{LaAlO}_3$ seeds with iridium holder	20
5	Single crystal of $\text{LaAl}_{0.9}\text{Sc}_{0.1}\text{O}_3$	22
6	Single crystal of $\text{LaAl}_{0.75}\text{Sc}_{0.25}\text{O}_3$ grown off stoichiometry	24
7	Single crystal of $\text{LaAl}_{0.75}\text{Sc}_{0.25}\text{O}_3$ grown with correct melt formulation	25
8	Lattice Constants of $\text{LaAl}_{1-x}\text{Sc}_x\text{O}_3$ Mixed Crystals	29
9	Compositions Investigated in the $\text{La}_2\text{O}_3$ - $\text{Al}_2\text{O}_3$ - $\text{Sc}_2\text{O}_3$ System	30
10	Example of grown crystal from Run La-10	35

## LIST OF TABLES

<u>Table</u>	<u>Title</u>	<u>Page</u>
I	Materials Used in Program	6
II	Summary of Crystal Growth Runs	27
III	X-ray Data for Pure $\text{LaAlO}_3$	32
IV	X-ray Powder Data for Sample La-11	33





## FOREWORD

This annual summary report describes research efforts on the preparation of single crystal mixed perovskite laser hosts. All crystals were doped with  $\text{Ce}^{3+}$  in an attempt to obtain blue-green lasers which may operate near 485 nm. The report relates work started in the period of October 1, 1982 and up to January 31, 1984. All work was done under Contract N 00014-83-C-0072. The research was coordinated under a program of Dr. Van O. Nicolai of the Office of Naval Research.

All physical preparations were completed in the laboratories of Airtron Division of Litton Industries, 200 E. Hanover Avenue, Morris Plains, New Jersey 07950. The program was directed by Dr. Roger F. Belt and Mr. Robert Uhrin served as Senior Staff Engineer. Ms. Karen Grimes was the technician. Some optical tests were performed at the Naval Research Laboratory through the courtesy of Dr. Leon Esterowitz. The x-ray patterns were run by Mr. John Yorston. The report was prepared by Dr. Roger Belt and Mr. Robert Uhrin. It was released for publication in February, 1984.

## ABSTRACT

Mixed crystals of the perovskite type structures of the system  $\text{La Al}_{1-x} \text{Sc}_x \text{O}_3$  were examined over the compositions of  $x = 0.15 - 0.30$ . Single crystals were grown from melts in iridium crucibles using the Czochralski method. Seed crystals of {111} pure  $\text{La Al O}_3$  were used. The growth atmosphere was controlled at 99.75% of  $\text{N}_2$  and 0.25%  $\text{H}_2$ . Dopants of  $\text{Ce}^{3+}$  were maintained at 0.01 - 0.05 atomic per cent. Preliminary work on polycrystalline materials showed that blue-green luminescence at 485 nm was found. The grown crystals had various amounts of Sc incorporated and were usually translucent. At the  $x = .30$  formulation of melt, about 60 - 75% of Sc is believed to enter the crystal. No direct evidence was found for ordered type structures. The phase data, compositions, crystal quality, luminescence data, and x-ray results are discussed.

## 1.0 Introduction

Solid state lasers which operate in the blue-green have been a major goal of the Navy for many years. The search for these has centered on the discovery of ideal host crystals which will provide luminescence at desirable wavelengths when doped with particular rare earth ions. The latter are ions which are capable of  $4f \rightarrow 5d$  transitions. They include  $Ce^{3+}$ ,  $Eu^{2+}$ ,  $Pr^{3+}$ ,  $Tm^{3+}$ ,  $Er^{3+}$ , or  $Nd^{3+}$  which have symmetry allowed broad bands. These potential lasers can be pumped with broad band sources and may even be tunable under some circumstances. The simplest ion to work with has been  $Ce^{3+}$  since it possesses only one  $4f$  electron. The luminescence of  $Ce^{3+}$  in various host crystals has been studied for many years because of applications to CRT phosphors, lasers, and radiation detectors. It is well known that the emission of  $Ce^{3+}$  is broad band and very sensitive to the primary coordination, i.e., the exact crystal structure of the host. The early work of Blasse<sup>1,2</sup> showed that both ultra-violet emission around 300-400 nm and visible emission near 525-625 nm are possible. The energy level splitting for  $5d^1$  levels is actually reversed for octahedral and cubic coordination. The appropriate shifts in emission wavelengths are generated mainly through the cubic and highly symmetric laser hosts. However, one must avoid excited state absorption<sup>3</sup>, similar to what occurs in  $Ce^{3+}$ :YAG. This suggests a high band gap host prefer-

ably above  $50,000\text{ cm}^{-1}$  (6.2 eV). Early work at Airtron and other laboratories suggest that continued investigations with perovskite structures offer good possibilities for blue-green lasers.

An ideal laser host for blue-green operation should have the following properties:

1. The luminescence with  $\text{Ce}^{3+}$  or other rare earth should be centered around 450 - 500 nm. This suggests the near cubic site symmetry; the crystal structure need not be cubic.
2. The host band gap should be 6 eV or higher for oxide or fluoride.
3. A high radiative lifetime and high fluorescent quantum yield for  $\text{Ce}^{3+}$  or the rare earth are desirable.
4. Incorporation of a single oxidation state if  $\text{Ce}^{3+}$  is used, thus a minimum of  $\text{Ce}^{4+}$ .
5. Freedom from severe color center formation or defect oxide production during growth or optically pumping should occur.
6. A hard, refractory, chemically inert, large single crystal must be grown in high optical quality. No difficulties should occur with crucibles, phase relations, or atmospheres of growth.

7. The crystal should be grown preferably by the Czochralski method in available commercial equipment.

Nearly two years ago Airtron began preliminary work on mixed perovskites for laser hosts. The perovskite structure was chosen because of the unique coordination in the prototype  $\text{ABO}_3$  compound. Most perovskites<sup>4</sup> are cubic crystal structure or through slight distortions, may possess a lower symmetry hexagonal or orthorhombic variation. In the normal  $\text{ABO}_3$  type perovskite, the A ion possesses a coordination of 12 oxygen ions while the B ion has 6 oxygen ions. The combined charges of the A and B ions is six; thus many new combinations are possible where A is of valence 1, 2, and 3 and B is of valence 5, 4, 3 respectively. Naturally A and B can be simple ions or several sub-ions in proper amounts to maintain overall charge balance. It is appropriate to search for those perovskites which may retain the ideal cubic crystal structure. However, the coordination of the doping ion and its environment (near neighbors and second near neighbors) actually determine the precise position of fluorescent emission bands. It is of utmost importance to avoid phase transitions, twinning, or other structural behavior which may render the crystal difficult to grow or impossible to use. Thus the important host crystal  $\text{La Al O}_3$  very early was found<sup>5</sup> to have a phase transformation and twins. The latter were always detrimental to high laser

rod quality<sup>6</sup>.

Our first perovskites involved compositions of the type  $\text{La}_{.5} \text{Ba}_{.5} \text{Ta}_{.25} \text{Al}_{.75} \text{O}_3$  doped with 0.01%  $\text{Ce}^{3+}$  introduced as  $\text{Ce O}_2$ . However, these proved to be difficult to grow in pure form by means of the Czochralski method. Furthermore, the fluorescence emission of even the polycrystalline material occurred in the orange region (580-620 nm) under ultraviolet excitation. Attempts were made in growth under  $\text{N}_2$  and  $\text{H}_2$  atmospheres. Even these failed to give any blue-green emission. This work was performed in the period of May - July, 1981. In September of that same year, the first experiments were performed on sintered powders in the  $\text{La Al}_{1-x} \text{Sc}_x \text{O}_3$  system doped with  $\text{Ce}^{3+}$ . These experiments were suggested by Dr. Van O. Nicolai of the Office of Naval Research. Our preparation of powders were done under a  $\text{N}_2 - \text{H}_2$  atmosphere and gave blue-green emission under ultraviolet excitation. A spectroscopic examination of these powders at the Naval Research Laboratory showed that luminescence was centered near 485 nm. From that date a thorough program was organized at Airtron to investigate the single crystal growth of  $\text{La Al}_{1-x} \text{Sc}_x \text{O}_3$  compounds. This report summarizes the efforts made through the December, 1983 period under a portion of our growth program.

## 2.0 Experimental Procedures

### 2.1 Materials for Compositions

The starting components for all of our single crystal

preparations are lanthanum oxide ( $\text{La}_2\text{O}_3$ ), aluminum oxide ( $\text{Al}_2\text{O}_3$ ), scandium oxide ( $\text{Sc}_2\text{O}_3$ ), and cerium oxide ( $\text{Ce O}_2$ ). The components were purchased from recognized vendors in a purity which is considered to be laser or luminescent grade. Table I gives a general summary of the pertinent data. Overall it is thought that  $\text{Sc}_2\text{O}_3$ , because of its limited industrial use, cost, and relative scarcity, has the greatest amount of impurity. The impurity range of most 99.99% rare earth oxides is about 100 ppm of other rare earth ions and 100-200 ppm of non-rare earths. The latter are principally  $\text{Ca}^{2+}$ ,  $\text{Mg}^{2+}$ ,  $\text{Si}^{4+}$ ,  $\text{Fe}^{3+}$ ,  $\text{Na}^{1+}$  and  $\text{Al}^{3+}$ . It is important to note that with the purity of our materials, there is probably no effect whatsoever on the phase behavior. Under any circumstances these impurity levels are not detected by X-ray diffraction procedures.

A further word must be said about the  $\text{Ce O}_2$  since the starting material is  $\text{Ce}^{4+}$  and the desired dopant is  $\text{Ce}^{3+}$  in the perovskite. In most oxide systems such as garnets, perovskites, or related structures the proportion of  $\text{Ce}^{3+}$  is thought to be high upon doping with  $\text{Ce O}_2$  and growing in less than 1% of  $\text{O}_2$ . It can be made higher by growing under a reducing gas like  $\text{H}_2$  or annealing the crystal in  $\text{H}_2$  after growth. The amount of  $\text{Ce}^{3+}$  can be maximized by doping with  $\text{Ce}_2\text{O}_3$  and growing in an inert or reducing gas. However the preparation of  $\text{Ce}_2\text{O}_3$  is a fairly complicated procedure. It is prepared by  $\text{H}_2$  or carbon reduction



TABLE I  
MATERIALS USED IN PROGRAM

<u>Component</u>	<u>Purities</u>	<u>Vendors</u>
$\text{La}_2\text{O}_3$	99.999%	United Mineral & Chemical
$\text{Al}_2\text{O}_3$	99.999%	Baikowski International
$\text{Sc}_2\text{O}_3$	99.99 %	United Mineral & Chemical
$\text{Ce O}_2$	99.999%	Spex Industries

of  $\text{Ce O}_2$  at  $1200^\circ \text{C}$  or higher. Once prepared it is fairly stable unless oxidized directly at high temperatures. In all of our experiments we have begun and retained the dopant with  $\text{Ce O}_2$ . Since the amount of dopant is 100 - 500 ppm, one can see that the  $\text{Ce O}_2$  should have no effect on phase behavior to a good approximation. However, the chemical state may influence the presence, intensity, or other factors associated strictly with the luminescent behavior.

## 2.2 Crucibles Used

The most useful crucibles for all of our preliminary work were constructed from 99.95% iridium metal. Crucibles were fabricated by Engelhard Industries. It should be realized that the melting points of our component oxides range from  $2050^\circ \text{C}$  to  $2400^\circ \text{C}$ . The perovskite compositions of interest probably melt at  $2050^\circ$ -  $2200^\circ \text{C}$ . Fortunately our early experiments showed that stable melts could be obtained for prolonged times without any damage to the crucible. In order to obtain a complete melt in a crucible, the wall temperature is about  $50^\circ$ -  $150^\circ$  hotter than the melt center. Iridium melts at  $2450^\circ \text{C}$ . The iridium crucible size was 2.00 inch diameter x 2.00 inches high with a volume of  $103 \text{ cm}^3$ . Wall thickness is 0.060 inch. All crucibles were used with lids which had a 1.25 inch circular hole for the crystal. There has been some discussion<sup>7</sup> that the presence of  $\text{Ir}^{4+}$  and  $\text{Fe}^{3+}$  may cause fluorescent quenching. This item is debatable but the growth

of crystals in molybdenum crucibles may be preferable for reducing atmospheres.

Crucibles prepared from molybdenum, tungsten, or tantalum are much more susceptible to oxidation than iridium. However the pure metals have melting points of 2610°C, 3410°C, and 2996°C, respectively. The metals are heated primarily under vacuum, in reducing gases such as H<sub>2</sub>, or in pure dry N<sub>2</sub>. We have attempted direct heating with 400 KHz RF in our standard growth furnaces. An atmosphere of 99.75% N<sub>2</sub> -0.25% H<sub>2</sub> was passed continuously through a sealed system. Our crucibles were made from molybdenum and were 2.00 inch diameter x 2.00 inch high x 0.090 inch wall. Similar ones were made in a 3 x 3 inch size. These were manufactured by Newark Spinning Co. from 99.95% metal. The first attempts were made by heating the bare crucible to about 2000° C in order to check for evidence of severe corrosion. Some oxide was formed but the crucible survived intact. By preparing a melt of La Al O<sub>3</sub> and running it at temperatures close to 2100° C, we demonstrated the integrity of the system. The general procedure on crucible choice was to perform all preliminary growth and phase behavior experiments in iridium. If and when luminescence quenching occurs, a switch to molybdenum can be made using the same melts and growth station geometry.

### 2.3 Seed Crystals

Our first compositions were prepared with the idea of

obtaining stable melts and attempted seeding on a bare iridium wire. The melts were brought to the position where a tiny island of solid material was evident on the melt surface. The temperature was increased until this last solid disappeared. The iridium wire was inserted and some crystallization always occurred. However the seeds were small and of an unknown and inconsistent orientation. Frequently a large polycrystalline mass was obtained. Better results were given by a piece of  $\text{La Al O}_3$  obtained from Crystal Systems of Salem, Massachusetts. This was a translucent piece of twinned crystal melted in a Mo crucible. The best and most consistent results were obtained from a clear twinned single crystal of pure  $\text{La Al O}_3$  grown by the Czochralski method. This crystal was about 4 - 5 mm diameter x 20 - 25 mm long and provided by Dr. Van Nicolai of ONR. The orientation was along [111] of the high temperature cubic phase. The crystal was used as received in the twinned state. This crystal always gave a seeded melt quickly and started growth with no complications. The seed was held in an iridium holder. The origin of this  $\text{La Al O}_3$  single crystal was from work <sup>8,9</sup> performed by Union Carbide under contract to ONR.

#### 2.4 Growth Station

The growth station used under this program was a typical RF heated Czochralski design similar to those used in the production of high melting oxide laser crystals. A picture of the actual station is given in Figure 1 while Figure 2 is a



Figure 1 Czochralski Growth Station

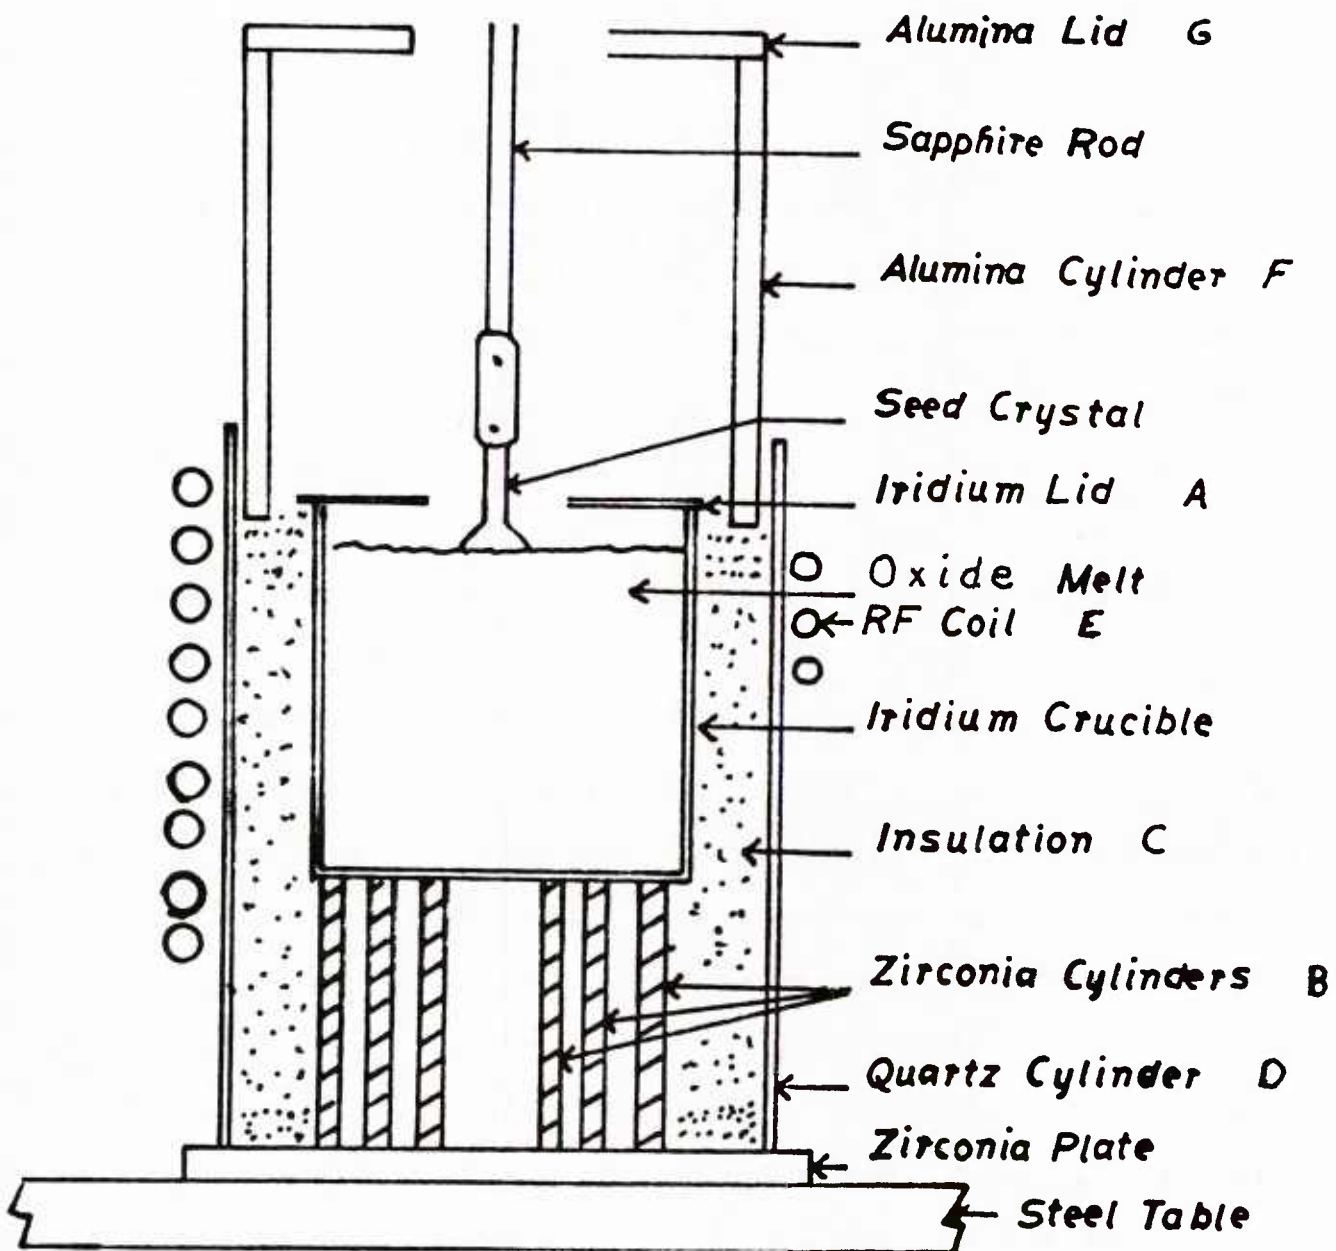


Figure 2 Drawing of Basic Growth Station

drawing of the crucible and insulating support materials. The RF unit is a Lepel Inc. 70 KVA, 400 KHz, commercial model culminating in a 10 turn copper coil. An optical pyrometer provided a signal used to control the diameter of the growing crystal. The crucible and appurtenances were surrounded with a sealed bell jar for atmosphere control. The growth gradient along the pulling direction was sufficient to get seeding initiated and crystals of 1-2 cm diameter x 5-10 cm could be grown without difficulty. Pulling and rotational mechanism arrangements are provided over a range of 0.1 - 10 cm/hr and 1-150 rpm respectively.

## 2.5 Run Technique

The general procedure for all runs remained the same. Preparations were chosen on the basis of the desired compositions. The pure oxides were weighed and mixed thoroughly. The oxides were packed in the crucible prior to each run. The melt volume and hence amount of the components was chosen to fill the crucible to about 80-90% of capacity at melt temperature. The crucible is placed in the station according to a precise and reproducible geometry. The bell jar is put over the system and gas flow is commenced. The crucible is brought to a temperature where all material is liquid. The seed crystal is then lowered into the melt and the latter is cooled to start growth. When growth starts satisfactorily, the control system is initiated and the crystal is brought out to the sought diameter. The crystal is



then pulled to total length. Usually the run is stopped with the grown crystal in contact with the melt to minimize thermal shock upon cooling. The station is programmed down from melting points of 2100-2200°C to 25°C over a period of several days. The crystal is removed by cutting or fracture at the bottom. The crucible is cleaned for the next run.

## 2.6 Crystal Compositions

Little or no previous work has been done on mixed perovskites involving the three component system<sup>10</sup> of  $\text{La}_2\text{O}_3$  -  $\text{Al}_2\text{O}_3$ - $\text{Sc}_2\text{O}_3$ . Only the two component systems are reported. The phase diagram is a serious omission and prevents one from going directly to a verified composition which will show some promise for growing a single crystal. In the absence of these data we have chosen to examine growth of single crystals in the formulation  $\text{La Al}_{1-x}\text{Sc}_x\text{O}_3$  where  $x$  lies in the range of 0.15-0.30. The only rational justification for this is the coincident report<sup>11</sup> of a composition near  $x=0.30$  made from sintered oxides at 1200°C (this composition was not a pure single phase as judged from the reported X-ray diffraction pattern). On the basis of size considerations it might also be argued that 25% substitution of Al by Sc might tend to give ordered cubic perovskites. However this is only suggested<sup>4</sup> and the highest degree of ordering is thought to occur when the two B ions are very different in size and charge. Galasso<sup>4</sup> does not report ordering

in our system but his book is complete to only 1970. Note that  $\text{Al}^{3+}$  and  $\text{Sc}^{3+}$  have the same charge and the ionic radii are 0.56A and 0.69A, respectively, as calculated by Geller<sup>12</sup> for  $\text{ABO}_3$  type compounds. As far as a laser host is concerned, the crystal can be ordered or unordered, cubic or any other system, and of any composition. However, it must fulfill the emission and quality requirements desired for blue-green crystal lasers.

## 2.7 Atmospheres for Growth

The choice of gas for growing any single crystal material is highly important. Ideally, oxides should be grown in  $\text{O}_2$ , fluorides in  $\text{F}_2$ , and so forth in order to prevent defects such as vacant lattice sites. The latter usually lead to color center phenomena which may interfere with absorption or emission. One must also recognize the effects of the growth atmosphere on the desired valence states of any components. For example, the  $\text{Ce}^{3+}$  is a dopant which is best stabilized by no oxidizing conditions. For our purposes, the gas has no effect on any phase behavior. We have chosen a mildly reducing gas mixture of  $\text{N}_2\text{-H}_2$  to introduce the  $\text{Ce}^{3+}$ . About 0.25-1.00% by volume of  $\text{H}_2$  is satisfactory. So far as is known, this has not generated color centers. However, large single crystals have not been examined optically. It is known that the change of gas or elimination of  $\text{H}_2$  will cause slight color shifts as observed visually. The use of large amounts of  $\text{H}_2$  or the presence of  $\text{H}_2\text{O}$  may introduce small

concentrations of  $\text{OH}^-$  into oxide crystals at high temperatures. The  $\text{OH}^-$  may act as a quenching center and affect fluorescent yields.

## 2.8 Doping Levels of $\text{Ce}^{3+}$

The ionic radius of  $\text{Ce}^{3+}$  is very close to that of  $\text{La}^{3+}$  and we have always assumed a distribution coefficient of 1.0 for  $\text{Ce}^{3+}$  introduction into our melts. The absolute concentration of  $\text{Ce}^{3+}$  in the melt was formulated to be 0.01 - 0.05 atomic %. This is a rather low concentration compared to most laser crystals which are doped at levels of 10-100 times higher than this. However, the absorption and emission bands of  $\text{Ce}^{3+}$  are very strong and 0.05% is sufficient. We have made no attempts to measure fluorescent lifetimes, or lifetime as a function of concentration. The dopant of  $\text{Ce}^{3+}$  at 0.05% is never detected in X-ray diffraction patterns. Because of its similarity in size and chemical activity to  $\text{La}^{3+}$ , we believe there is no effect on phase behavior in all our work. Therefore, all crystal preparations contained Ce.

## 2.9 Evaluation of Crystals

After a crystal was grown from a particular composition, the boule was separated from the seed and examined visually and microscopically. The color, crystallinity (single or polycrystalline), transparency, quality, and stability in light are noted. The crystal is examined under a short wavelength ultra-

violet lamp for color and brightness of fluorescence. The crystal is also sectioned into 1 mm disks. These disks are mechanically polished on both sides and examined in a polarizing microscope for structure, twinning, phase separation, and other artifacts. Finally, the crystal is sampled at the top and bottom for X-ray diffraction analysis. The latter provides direct evidence of structure, quality, phases, impurities, and incorporation of Sc by means of lattice constant. In some cases, the absorption and emission spectra were taken from polycrystalline powders. X-ray patterns were run over the full range of  $2\theta$  values from  $10 - 120^\circ$  with  $\text{Cu K}_\alpha$  radiation. Lattice constants were measured from resolved doublets at high  $2\theta$ . Both diffractometer and films were used to record patterns. The films were given exposures of 24 hours to detect any weak lines not apparent on a diffractometer trace. This is important especially for detection of small amounts of a new phase or evidence of ordering in perovskite compositions.

### 3.0 Results of Growth Runs

#### 3.1 Run Description

Two problems which had to be overcome initially in this program were (a) to obtain material from which seeds could be fabricated for use in later runs, and (b) to obtain doped crystalline material which exhibited the desired fluorescence. Since the presence of atomic iridium in the crystal was believed to quench the  $\text{Ce}^{+3}$  fluorescence, it was felt that in order to solve the latter problem, iridium crucibles should be avoided if possible. Additionally, it was felt to be advantageous to avoid iridium because of the high melting point of  $\text{La AlO}_3$  which requires the crucible to be driven near to its melting point. Consequently, the first growth experiment was made using a molybdenum crucible in an inert atmosphere of nitrogen containing approximately one percent hydrogen to control the valence state of cerium.

In spite of efforts to eliminate oxygen by purging and outgasing the system, it was not possible to grow using this arrangement. Extensive oxidation of the molybdenum occurred with the crucible glowing only red hot. Thus a completely closed system and inert environment are indicated.

The second growth experiment was designed to obtain single crystalline material from which to fabricate some seeds. The lack of success with molybdenum required that an iridium

crucible be used, but an approximately 0.25 percent hydrogen atmosphere was utilized to provide reducing conditions. An effort was made to obtain nucleation and growth on an iridium wire dipped into and pulled out of the melt, but, when this was unsuccessful, the entire melt was cooled with the wire in contact. This nucleation site allowed some single crystalline areas to develop as the melt cooled and slugs were core-drilled from these areas to obtain crystalline pieces for seeding. The cooled melt is exhibited in Figure 3. at the crucible bottom.

Following this experiment a makeshift iridium holder was fashioned and one of the pieces obtained in the previous growth run was used in an effort to obtain growth. This was only partially successful in that thermal asymmetry in the melt caused the growth to rotate eccentrically and prevent adequate control. Subsequently the melt was cooled with the seeded portion in contact and an improvement in the crystalline quality of the solidified melt was achieved. Crystalline pieces cut from the solidified melt as well as the iridium holder are exhibited in Figure 4.

In spite of these successes, it was felt that the low thermal gradient, the awkward shape of the seed holder and the size of the seeds obtained would preclude adequate control and quality of growth. At this point, a small  $\text{La Al O}_3$  crystal became available and this crystal was shaped to provide a good

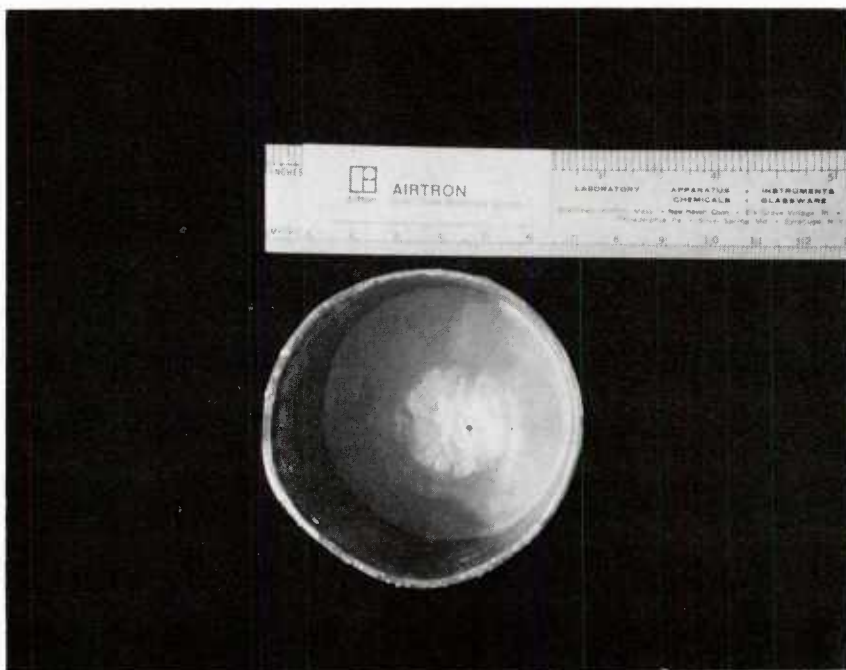


Figure 3. Crystallized melt obtained by seeding with an iridium wire.





Figure 4. Initial  $\text{La AlO}_3$  seeds with iridium holder.

quality seed of sufficient length. The fourth growth experiment utilized this seed to obtain the crystal exhibited in Figure 5. It should be noted that in this and the preceding experiments the melt composition was adjusted to provide a 10% substitution of scandium in the crystal. There was no immediate indication of any effect this might have had but the quality of growth was fairly good. Some cloudiness was evident but there was no indication of a tendency toward cracking.

The fifth growth experiment was designed to provide a 25% substitution of scandium in the crystal. In order to accomplish this, the melt from the previous growth run was compositionally adjusted by adding additional powder to the crucible. Unfortunately, the amount required to do this exceeded the capacity of the crucible and it became necessary to terminate the experiment and to clean the crucible.

The sixth growth run was again formulated to the 25% scandium substitution. The melt had very good convection characteristics and no difficulty was encountered in dipping the seed or initiating growth. However, at some point after the growth was put into its automatic mode, the crucible developed a leak and the growth was terminated.

The seventh growth run was intended to repeat the preceding experiment, but the crucible again developed a leak and it was necessary to terminate the run. Consequently, this

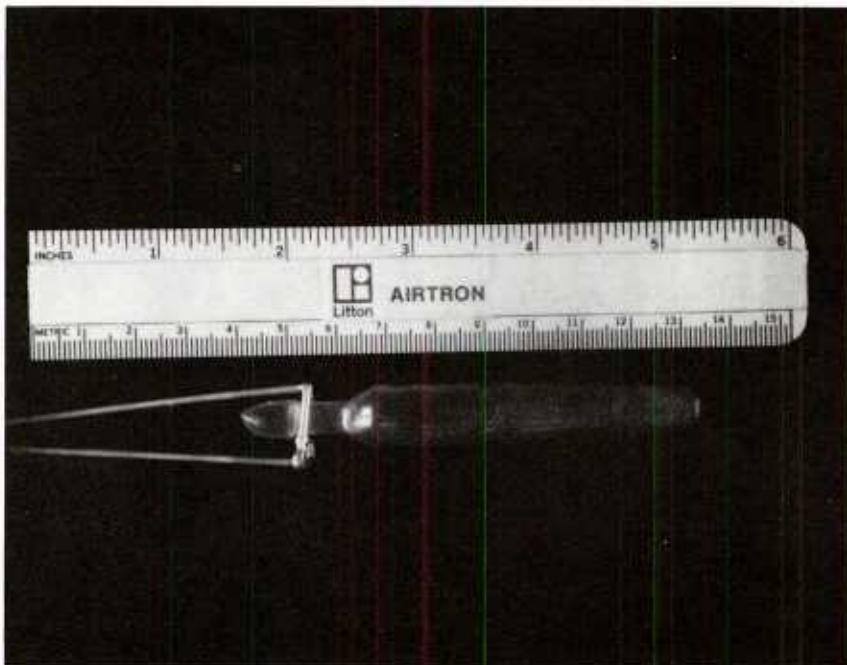


Figure 5. Single crystal of La Al<sub>0.9</sub> Sc<sub>0.1</sub> O<sub>3</sub>

experiment was carried over to the eighth growth run. Although the melt convection pattern looked good and the initial growth proceeded well, some problems were experienced in controlling the diameter in the automatic mode. It became necessary to control the growth manually in order to obtain sufficient growth on which to perform some x-ray measurements. Following termination of the growth cycle, the crystal assumed an opaque appearance characteristic of particulate inclusions (Figure 6). It appeared to be single crystalline although twinned.

At this point in the program, it was determined that the composition of the previous melts was determined incorrectly so that growth was carried out from what would appear to be incongruently melting alumina rich compositions. The x-ray data indicated that single crystalline  $\text{LaAlO}_3$  was obtained but that the amount of scandium substitution was relatively small. An adjustment was made to achieve the 25% substitution in the ninth growth run, but after several growth attempts, the crucible leaked again.

The tenth growth experiment achieved the objective of obtaining a crystal having the desired 25% substitution. The growth quality was not good but it was improved over that achieved in the eighth growth run. The x-ray data also confirmed that the scandium was now entering the crystal lattice as anticipated. This crystal can be observed in Figure 7.

The eleventh growth run carried the experiments one

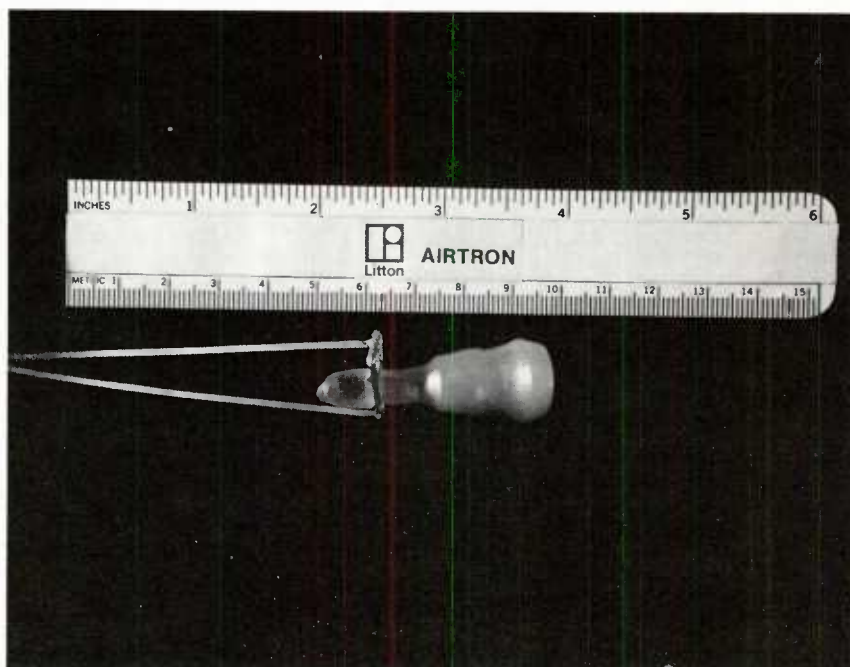


Figure 6. Single crystal of  $\text{La Al}_{0.75} \text{Sc}_{0.25} \text{O}_3$  grown off stoichiometry

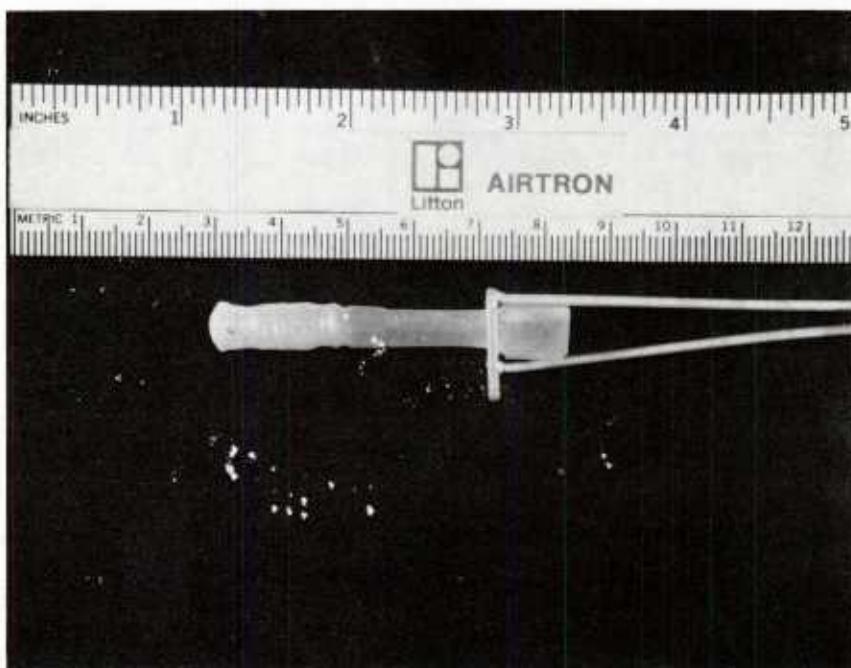


Figure 7. Single crystal of  $\text{LaAl}_{0.75}\text{Sc}_{0.25}\text{O}_3$  grown with a correct melt formulation.

step further in that it was designed to accomplish a 30% substitution of scandium. As in previous runs, it appeared to be a single crystal but was opaque. However, x-ray measurements showed that a further substitution of scandium had occurred.

The growth experiments did not result in any high quality growth, but they did provide enough information to indicate a probable compositional region in which to work. It is felt that better results would have been achieved with better quality seeds and that further work at some fixed composition should result in that end. This would at least provide better material with which to carry out further growth experiments. Results of the growth experiments and growth conditions are summarized in Table II. It should be noticed that the crystal compositions were those originally formulated for the melt. They are not the actual analyzed composition of the grown crystal. It appeared that a distribution coefficient of 0.7 for  $\text{Sc}(\text{crystal})/\text{Sc}(\text{melt})$  is operative. All crucibles were iridium except for the first attempt. Some runs were attempted at both the 1.5 mm/hr pull rate and a slower one of 0.5 mm/hr to improve quality. However this made little difference in the cloudy appearance of the crystal.



TABLE II

## SUMMARY OF CRYSTAL GROWTH RUNS

RUN #	CRYSTAL COMPOSITION DESIRED	CRUCIBLE MAT'L	PULL RATE (mm/hr)	ATMOSPHERE	COMMENTS
LA-1	LaAl <sub>0.9</sub> Sc <sub>0.1</sub> O <sub>3</sub>	Molybdenum	--	1.1% H <sub>2</sub>	Unable to Melt material due to excessive crucible oxidation
LA-2	LaAl <sub>0.9</sub> Sc <sub>0.1</sub> O <sub>3</sub>	Iridium	--	0.25% H <sub>2</sub>	Melt solidified for seed material
LA-3	LaAl <sub>0.9</sub> Sc <sub>0.1</sub> O <sub>3</sub>	Iridium	--	0.1% H <sub>2</sub>	Melt crystallized with single crystal piece in contact
LA-4	LaAl <sub>0.9</sub> Sc <sub>0.1</sub> O <sub>3</sub>	Iridium	1.5	0.1% H <sub>2</sub>	Translucent crystal of fair quality obtained
LA-5	LaAl <sub>0.75</sub> Sc <sub>0.25</sub> O <sub>3</sub>	Iridium	--	0.1% H <sub>2</sub>	Run terminated due to inability to adjust melt composition
LA-6	LaAl <sub>0.75</sub> Sc <sub>0.25</sub> O <sub>3</sub>	Iridium	--	0.1% H <sub>2</sub>	Run terminated by crucible failure
LA-7	LaAl <sub>0.75</sub> Sc <sub>0.25</sub> O <sub>3</sub>	Iridium	--	0.1% H <sub>2</sub>	Run terminated by crucible failure
LA-8	LaAl <sub>0.75</sub> Sc <sub>0.25</sub> O <sub>3</sub>	Iridium	1.5	0.1% H <sub>2</sub>	Opaque single crystal obtained
LA-9	LaAl <sub>0.75</sub> Sc <sub>0.25</sub> O <sub>3</sub>	Iridium	--	0.1% H <sub>2</sub>	Run terminated by crucible failure
LA-10	LaAl <sub>0.75</sub> Sc <sub>0.25</sub> O <sub>3</sub>	Iridium	--	0.1% H <sub>2</sub>	Translucent crystal of poor quality obtained
LA-11	LaAl <sub>0.75</sub> Sc <sub>0.25</sub> O <sub>3</sub>	Iridium	--	0.1% H <sub>2</sub>	Opaque single crystal obtained

### 3.2 X-Ray Data

In the absence of firm phase diagram studies, most of our information had to be obtained empirically from the crystal growth runs. The use of X-ray diffraction patterns is indispensable in judging what phases, crystal structures, or other phenomena may be present. Thus each grown crystal was sampled at the top of the boule and an X-ray diffractometer trace was run well into the high  $2\theta$  region. Since it was important to determine the presence of impurities in low concentration, many X-ray patterns were obtained also by film procedures. The latter were taken with exposures up to five times normal in order to verify the presence of very weak lines unambiguously.

Figure 8 shows the compositions we have investigated in the three component system of  $\text{La}_2\text{O}_3$ - $\text{Al}_2\text{O}_3$ - $\text{Sc}_2\text{O}_3$ . Most of these are located near the  $\text{LaAlO}_3$  compound since increasing amounts of  $\text{Sc}_2\text{O}_3$  were added normally to the melt in each run. The first few runs did indeed show that in the crystal, increasing amounts of  $\text{Sc}_2\text{O}_3$  were incorporated. This was verified by the expanded lattice constant of the compositions. It should be recalled that the normal room temperature crystal form of  $\text{LaAlO}_3$  is rhombohedral. If we assume that this structure is retained approximately with little difference in angle, then a "lattice constant" - composition curve may be constructed as in Figure 9. The largest value of the lattice constant we have observed is about 3.85 Å which corresponds to an x of 0.25-0.30 in the formulation  $\text{LaAl}_{1-x}\text{Sc}_x\text{O}_3$ .

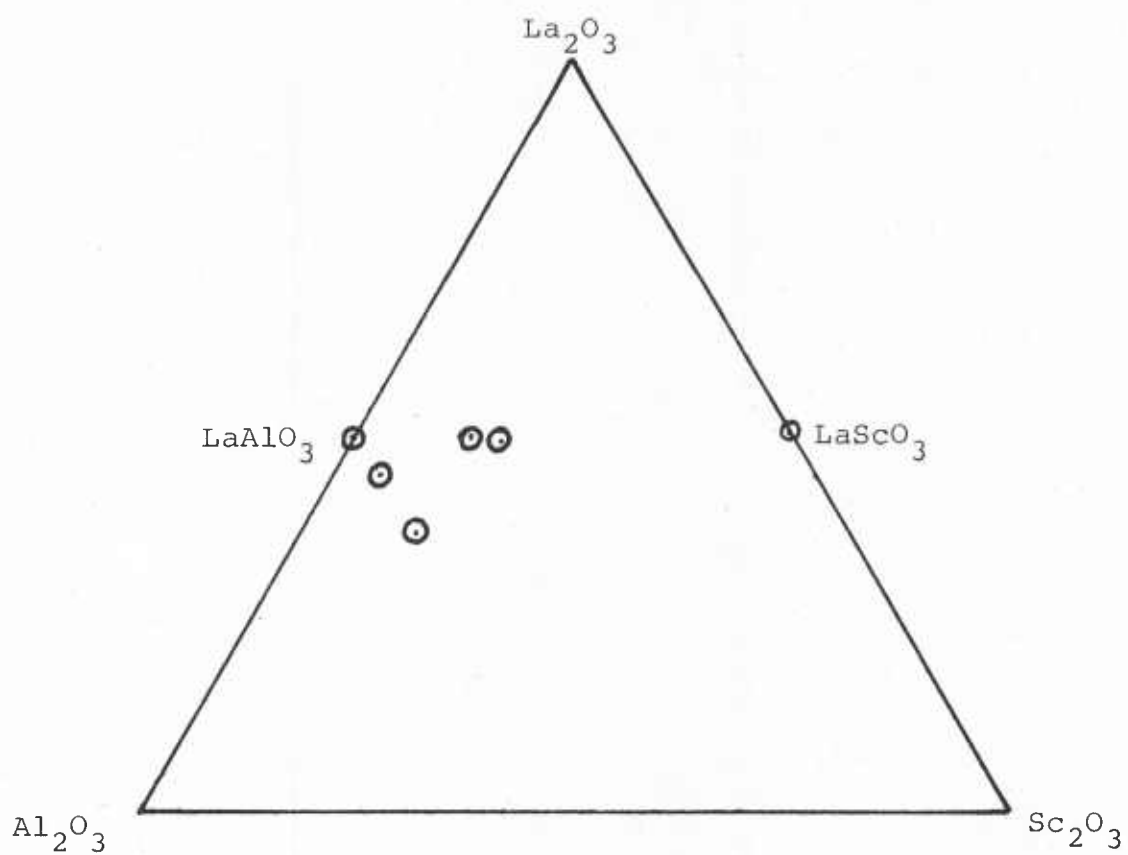


Figure 8 Compositions Investigated  
in the  $\text{La}_2\text{O}_3$  -  $\text{Al}_2\text{O}_3$  -  $\text{Sc}_2\text{O}_3$  System

Lattice Constant (A)

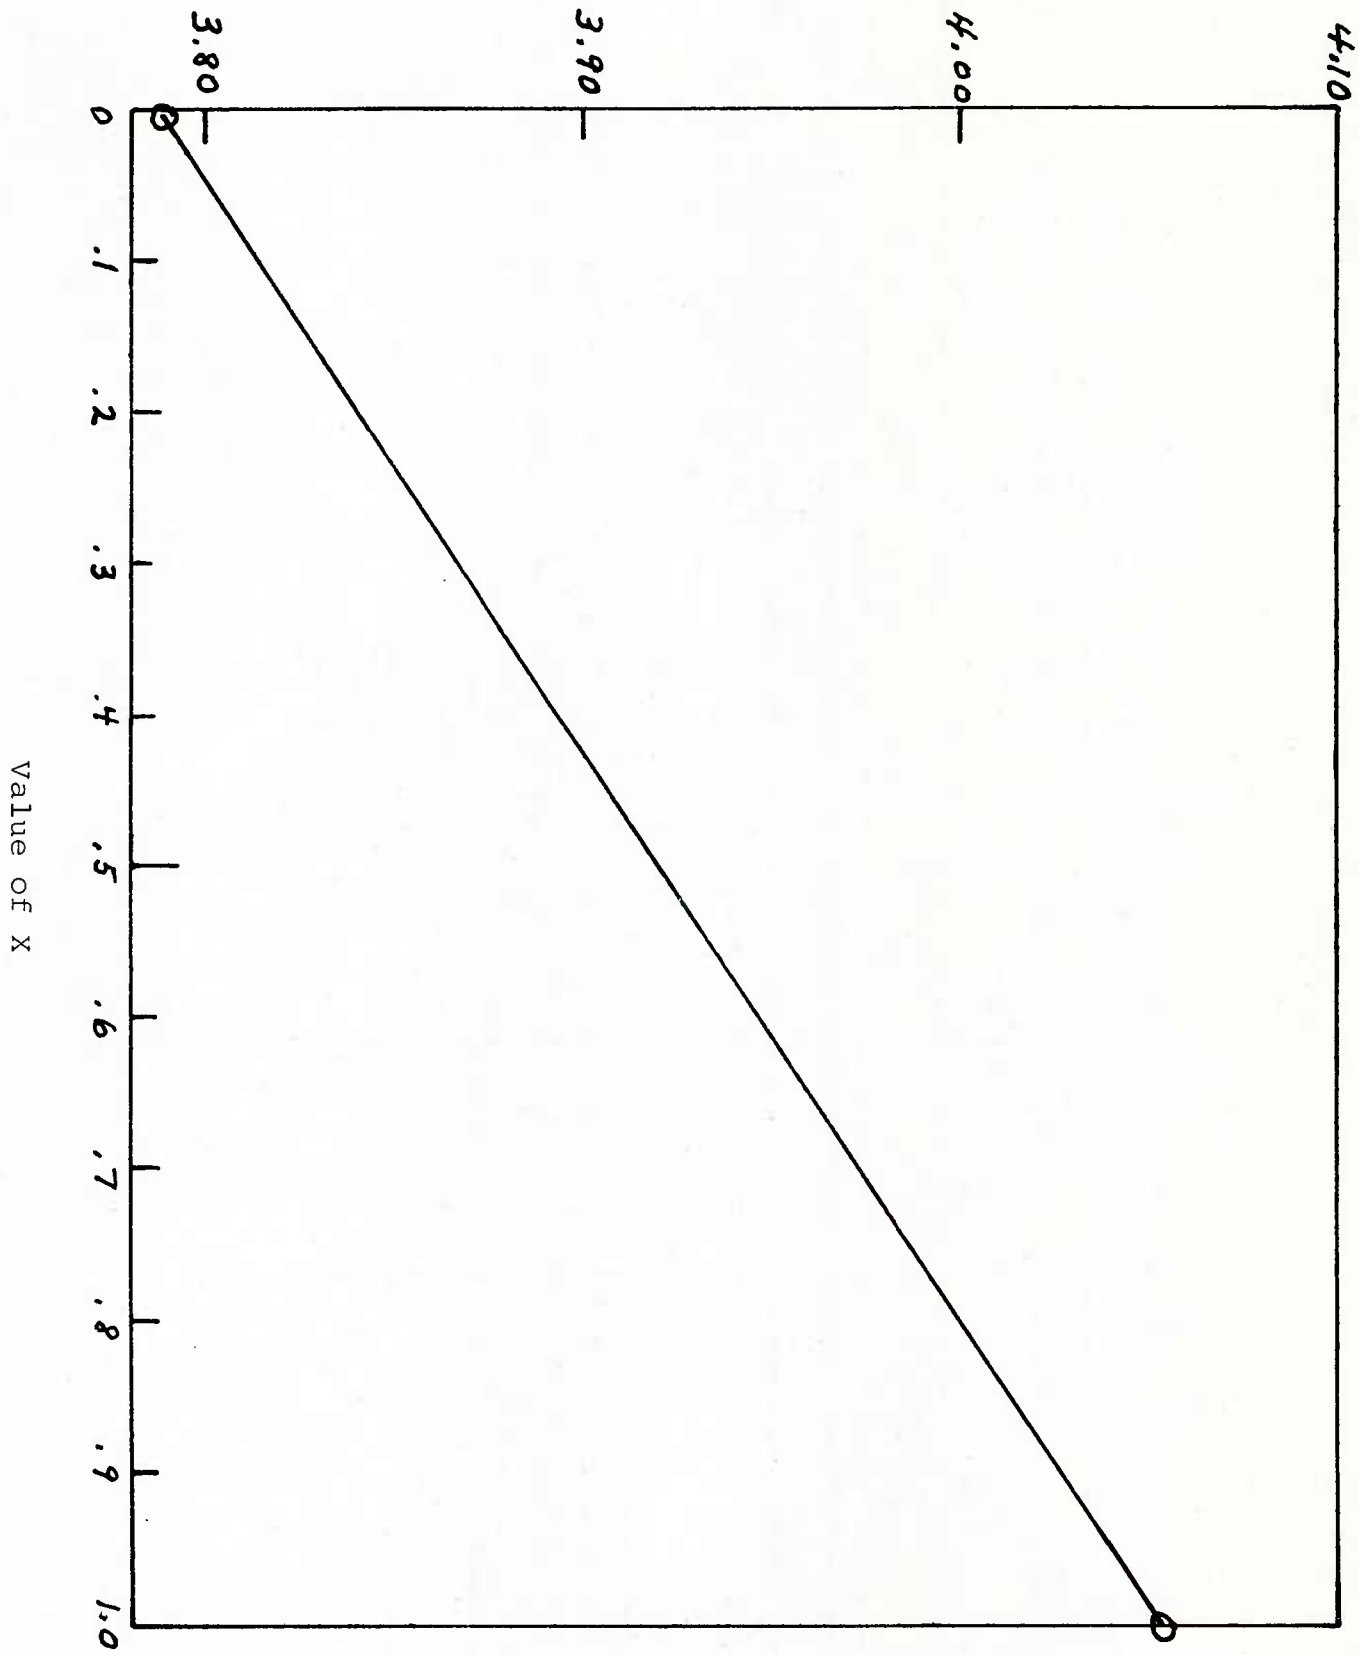


Figure 9 - Lattice Constants of  $\text{LaAl}_{1-x}\text{Sc}_x\text{O}_3$  Mixed Crystals

The actual values of  $x$  in the melt are larger than in the crystal which suggests that an effective distribution coefficient of 0.6-0.7 is necessary for  $k_{SC}$ . At the highest values of  $x$  in the melt, it appears that a two phase liquid is obtained and any single crystal growth becomes difficult.

We reproduce in Table III some pertinent X-ray powder data. The values in columns 1 and 2 are experimental ones taken from a pure phase of  $\text{LaAlO}_3$ . In fact these were taken from our seed crystal and they agree perfectly with the reported data of Geller and Bala.<sup>5</sup> The values of columns 3 and 4 are calculated from the cubic pseudo cell which corresponds to a cubic perovskite material. Note that the true symmetry is rhombohedral and only at elevated temperatures is there a transition to the cubic phase. The data in columns 5 and 6 are calculated from an expanded cubic unit cell of larger dimensions. These of course do not fit the room temperature data but are listed for reference. Table IV is a film powder pattern taken at a long exposure to develop any weak lines. Notice that several of these are obtained at low  $2\theta$  angles. It is interesting to note that this pattern is from a cloudy but good single crystal. None of the weak or extra lines in the pattern correspond to the strong X-ray lines of the starting components or other combinations. Thus the pattern is due to the crystal but with some modification of the structure beyond the normal rhombohedral. The most troublesome features are the four very weak lines beyond the 3.85 Å strong line. The latter is almost

Table III  
X-ray Data for Pure  $\text{LaAlO}_3$

Rhomb. hkl	d obs.	d calc. from ao=3.797	Closest Cubic kkl	d calc from ao=7.583	Cubic hkl
110	3.797	3.797	100	4.378	111
$\left. \begin{matrix} 10\bar{1} \\ 211 \end{matrix} \right\}$	2.657	2.685	110	3.792	200
$\left. \begin{matrix} 11\bar{1} \\ 210 \end{matrix} \right\}$	2.286			2.680	220
$\left. \begin{matrix} 200 \\ 222 \end{matrix} \right\}$				2.286	311
220	2.188	2.192	111	2.189	222
220	1.896	1.899	200	1.896	400
$\left. \begin{matrix} 20\bar{1} \\ 311 \end{matrix} \right\}$	1.736			1.740	331
$\left. \begin{matrix} 21\bar{1} \\ 321 \end{matrix} \right\}$	1.696	1.698	210	1.696	420
$\left. \begin{matrix} 2\bar{1}\bar{1} \\ 310 \end{matrix} \right\}$	1.548	1.550	211	1.548	422
$\left. \begin{matrix} 332 \\ 20\bar{2} \end{matrix} \right\}$	1.342	1.342	220	1.459	511
$\left. \begin{matrix} 422 \\ 30\bar{1} \end{matrix} \right\}$	1.339			1.459	333
$\left. \begin{matrix} 330 \\ 411 \end{matrix} \right\}$	1.264	1.266	300	1.340	440
$\left. \begin{matrix} 433 \\ 32\bar{1} \end{matrix} \right\}$	1.199	1.201	310	1.264	600
				1.214	531
				1.199	620

Table IV  
X-ray Powder Data for Sample La-11

<u>Observed d (Å)</u>	<u>Intensity</u>	<u>Calculated d a = 5.444 Å = 60.1°</u>	<u>hkl</u>
8.733	vvw		
7.158	vvw		
6.242	vvw		
5.038	vvw		
3.853	vs	3.853	110
3.022	vvw		
2.719	vvs	2.722	211
2.321	vvw	2.323	210
2.233	vs	2.225	200
2.213	w		
1.929	vs	1.926	220
1.725	ms	1.767	311
		1.722	321
1.579	vs	1.573	310
1.568	mw		
1.368	m	1.363	20 $\bar{2}$
1.361	m	1.361	422
1.289	mw	1.284	411
1.221	s	1.219	32 $\bar{1}$
1.165	mw		
1.117	w		
1.111	vw		



always the strongest and largest d spacing in any of the perovskite like structures. In addition to these four weak lines, there are several other weak additional lines at various spacings. These weak lines do not correspond to any of the components. Furthermore the strong line at 1.724 Å does not show good agreement with calculated data. Part of this may be due to the angle chosen for  $\alpha$ . However a more radical change in structure is suggested.

### 3.3 Visual and Microscopic

It was mentioned above that all of the grown crystals were of one detectable phase by X-ray diffraction. Visually, the crystals were not clear enough to get light through. In fact, they were never as clear as the original seed of  $\text{La Al O}_3$  even though the latter contained a large number of micro twins. A good example of the type of crystal we obtained is given in Figure 10. Other examples are evident in some of the previous photographs of growth runs.

In order to examine the single crystals, they were sectioned in a 1mm slice cut normal to the growth axis. The pieces were polished to a window specification with common abrasives in our polishing facility. Under a microscope, small scattering sites could be seen. These were similar to effects observed previously in  $\text{Y Al O}_3$  and must be attributed to small amounts of an alternate phase. Crystal compositions which were prepared at another contractor showed the same behavior below the melting point,<sup>13</sup> It is also obvious from both the X-ray and microscope data that none of the prepared compositions were cubic at room temperature.

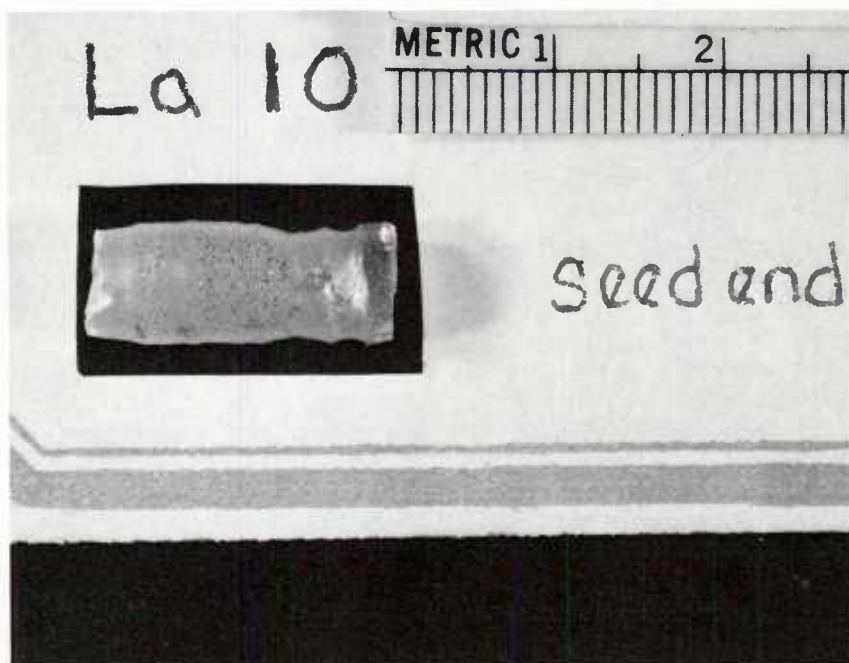


Figure 10. Example of grown crystal from Run  
La-10

### 3.4 Discussion

It is difficult to assign all the reasons for not obtaining a cubic phase in the  $\text{La Al}_{1-x}\text{Sc}_x\text{O}_3$  system. One of the fundamental criteria for a stable cubic structure is the Goldschmidt<sup>14</sup> tolerance factor  $t = (R_A + R_B) / \sqrt{2} (R_A + R_B)$  where  $R_A$  is the radius of the 12 coordinated cation (La) and  $R_B$  is the radius of the 6 coordinated cation (Al or Sc). For a stable range,  $t$  must be  $0.8 \leq t \leq 0.9$ . If the  $R_{\text{La}} = 1.14$ ,  $R_{\text{Al}} = 0.56$ , and  $R_{\text{Sc}} = 0.69 - 0.75$ , then  $t = 0.92$  for  $\text{La Al O}_3$ ,  $t \geq 0.96$  for  $\text{La Sc O}_3$ . Thus, for the mixed crystal of  $\text{La Al Sc O}_3$ , it would appear that  $t$  value is borderline or exceeds the desired value. It should be remembered that the ionic radii are preferably derived from X-ray data taken on actual perovskite materials. The paucity of data for Sc leaves some doubt as to what its radius actually is when combined with different elements. Even the mineral perovskite ( $\text{Ca Ti O}_3$ ) does not have a cubic structure. The analog  $\text{Sr Ti O}_3$  does and it has a  $t$  of 0.86. Since most tolerance rules are based on hard sphere packing, they are only approximate; the nature and type of bonding is also important.

It also appears that ordering phenomena appear more readily in compounds where the charge of the various B ions is different; for example the  $\text{Al}^{3+}$  and  $\text{Sc}^{3+}$  are similar whereas a  $\text{Mg}^{2+} + \text{Ge}^{4+}$  pair may order easily. Again, the charge type may influence the crystal structure more than a simple space consideration. Complex perovskites such as  $\text{Ba (Y}_{0.5}\text{Ta}_{0.5}) \text{O}_3$  and  $\text{Ba (Mg}_{0.33}\text{Ta}_{0.67}) \text{O}_3$  show a considerable degree of ordering. It should be noted that ordering can

### 3.4 Discussion - (Continued)

occur not only in cubic structures but other ones just as well. For purposes of obtaining correct fluorescence emission, it is preferred to have a precise crystal field with no complicating distortions.

### 3.5 Recommendations

Literally hundreds of compounds are possible with the perovskite ( $\text{ABO}_3$ ) crystal structure or a distorted variation of it. Thus, we can recommend that a careful approach must be made with those compounds, which to a first approximation, may give a cubic crystal structure from ion size considerations. Combinations of La, Gd, Y, Sc, Lu for A ions must be sought to give a high band gap host. The remaining ions of Al, Ga, Sc, or In are used as B ions to adjust melting range. Ideally, the materials for most perovskites can be prepared first in polycrystalline form. The presence of a cubic or other phase can be checked by X-ray diffraction. If results are positive, then the phase diagram should be investigated further. Finally, the single crystal growth should be attempted when enough knowledge is available on phase behavior. It should be realized that the  $\text{Ce}^{3+}$  emission in these preparations must center near 485nm. Fortunately, the fluorescence spectra can be obtained early enough on the polycrystals.

### 4.0 Conclusions

The  $\text{La Al}_{1-x}\text{Sc}_x\text{O}_3$  system has been investigated as a likely host crystal to give blue-green emission when doped

#### 4.0 Conclusions - (Continued)

with  $\text{Ce}^{3+}$  Nearly 10-12 attempts were made to grow single crystals over a compositional range up to  $x=0.3$ . Seed crystals of pure  $\text{La Al O}_3$  were used in  $[111]$  orientation. In all crystals, trace amounts of an apparent second phase were the principal problems. Even at slow growth rates, cloudy crystals were obtained which greatly impaired the optical quality for laser purposes. The complete phase diagram was not determined for the three component system  $\text{La}_2\text{O}_3\text{-Al}_2\text{O}_3\text{-Sc}_2\text{O}_3$  but it appears that the growth problems are too severe for meaningful improvements. The full exploitation of the perovskite structure still offers hope for cubic mixed crystals which may fulfill conditions for a satisfactory laser host.

#### REFERENCES

1. G. Blasse and A. Bril, J. Chem. Phys. 47, 5139 (1967).
2. A. Bril, G. Blasse and J.A. de Poorter, J. Electrochem. Soc. 117, 346 (1970).
3. W.J. Miniscalco, J.M. Pellegrino, and W.M. Yen, J. Appl. Phys. 49, 6109 (1978).
4. F.S. Galasso, "Structure, Properties and Preparation of Perovskite Type Compounds", Pergamon Press, New York, 1969.
5. S. Geller and V.B. Bala, Acta Cryst. 9, 1019 (1956).
6. H. Fay and C.D. Brandle, J. Appl. Phys. 38, 3405 (1967).
7. Ji. Kvapil, Jo. Kvapil, B. Manek, B. Perner, R. Autrata and P. Schauer, J. Crystal Growth 52, 542 (1981).
8. H. Fay and C.D. Brandle, Contract NONR-4793 (00) A1, (1965).
9. H. Fay and C.D. Brandle, Crystal Growth, Supplement to J. Phys. Chem. Solids, Pergamon Press, 1967, p.51.
10. E.M. Levin and H.F. McMurdie, "Phase Diagrams for Ceramists," The American Ceramic Society, Columbus, Ohio, Volume I and Supplements.
11. R.D. Rauh and A.N. Scovil, Report N00014-82-C-0142, July, 1982, EIC Laboratories, Inc., Newton, Mass. 02158
12. S. Geller, Acta Cryst. 10, 248 (1957).
13. Private communication from G. Khattak of Crystal Systems, Salem, MA.
14. V.M. Goldschmidt, Skriften norske Videnskaps Akad. Oslo I Mat. Natwiv, Kl. No. 8 (1926).

February 1982

REPORTS DISTRIBUTION LIST FOR ONR PHYSICS PROGRAM OFFICE  
UNCLASSIFIED CONTRACTS

Director Defense Advanced Research Projects Agency Attn: Technical Library 1400 Wilson Blvd. Arlington, Virginia 22209	3 copies
Office of Naval Research Physics Program Office (Code 421) 800 North Quincy Street Arlington, Virginia 22217	3 copies
Office of Naval Research Director, Technology (Code 200) 800 North Quincy Street Arlington, Virginia 22217	1 copy
Naval Research Laboratory Department of the Navy Attn: Technical Library Washington, DC 20375	3 copies
Office of the Director of Defense Research and Engineering Information Office Library Branch The Pentagon Washington, DC 20301	3 copies
U. S. Army Research Office Box 12211 Research Triangle Park North Carolina 27709	2 copies
Defense Technical Information Center Cameron Station Alexandria, Virginia 22314	12 copies
Director, National Bureau of Standards Attn: Technical Library Washington, DC 20234	1 copy
Commanding Officer Office of Naval Research Western Regional Office 1030 East Green Street Pasadena, California 91101	3 copies
Commanding Officer Office of Naval Research Eastern/Central Regional Office 666 Summer Street Boston, Massachusetts 02210	3 copies



Director U. S. Army Engineering Research and Development Laboratories Attn: Technical Documents Center Fort Belvoir, Virginia 22060	1 copy
ODDR&E Advisory Group on Electron Devices 201 Varick Street New York, New York 10014	3 copies
Air Force Office of Scientific Research Department of the Air Force Bolling AFB, D. C. 22209	1 copy
Air Force Weapons Laboratory Technical Library Kirtland Air Force Base Albuquerque, New Mexico 87117	1 copy
Air Force Avionics Laboratory Air Force Systems Command Technical Library Wright-Patterson Air Force Base Dayton, Ohio 45433	1 copy
Lawrence Livermore Laboratory Attn: Dr. W. F. Krupke University of California P.O. Box 808 Livermore, California 94550	1 copy
Harry Diamond Laboratories Technical Library 2800 Powder Mill Road Adelphi, Maryland 20783	1 copy
Naval Air Development Center Attn: Technical Library Johnsville Warminster, Pennsylvania 18974	1 copy
Naval Weapons Center Technical Library (Code 753) China Lake, California 93555	1 copy
Naval Training Equipment Center Technical Library Orlando, Florida 32813	1 copy
Naval Underwater Systems Center Technical Center New London, Connecticut 06320	1 copy

Commandant of the Marine Corps Scientific Advisor (Code RD-1) Washington, DC 20380	1 copy
Naval Ordnance Station Technical Library Indian Head, Maryland 20640	1 copy
Naval Postgraduate School Technical Library (Code 0212) Monterey, California 93940	1 copy
Naval Missile Center Technical Library (Code 5632.2) Point Mugu, California 93010	1 copy
Naval Ordnance Station Technical Library Louisville, Kentucky 40214	1 copy
Commanding Officer Naval Ocean Research & Development Activity Technical Library NSTL Station, Mississippi 39529	1 copy
Naval Explosive Ordnance Disposal Facility Technical Library Indian Head, Maryland 20640	1 copy
Naval Ocean Systems Center Technical Library San Diego, California 92152	1 copy
Naval Surface Weapons Center Technical Library Silver Spring, Maryland 20910	1 copy
Naval Ship Research and Development Center Central Library (Code L42 and L43) Bethesda, Maryland 20084	1 copy
Naval Avionics Facility Technical Library Indianapolis, Indiana 46218	1 copy